



# Standard Classification for E-CTFE-Fluoroplastic Molding, Extrusion, and Coating Materials<sup>1</sup>

This standard is issued under the fixed designation D 3275; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

*This standard has been approved for use by agencies of the Department of Defense.*

## 1. Scope \*

1.1 This classification covers melt processible molding, extrusion, and coating materials of ethylene-chlorotrifluoroethylene (E-CTFE) fluoroplastics. The resin is a copolymer of ethylene and chlorotrifluoroethylene containing approximately 80 weight % of chlorotrifluoroethylene.

1.2 The values stated in SI units, as detailed in IEEE/ASTM SI 10, are to be regarded as the standard.

1.3 The following precautionary statement pertains only to the test methods portion, Section 11 of this specification. *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

NOTE 1—Although this specification and ISO 12086-1 (1995) and ISO 12086-2 (1995) differ in approach or detail, data obtained using either are technically equivalent.

## 2. Referenced Documents

### 2.1 ASTM Standards:

D 150 Test Methods for A-C Loss Characteristics and Permittivity (Dielectric Constant) of Solid Electrical Insulating Materials<sup>2</sup>

D 618 Practice for Conditioning Plastics for Testing<sup>3</sup>

D 638 Test Method for Tensile Properties of Plastics<sup>3</sup>

D 792 Test Methods for Specific Gravity (Relative Density) and Density of Plastics by Displacement<sup>3</sup>

D 883 Terminology Relating to Plastics<sup>3</sup>

D 1238 Test Method for Melt Flow Rates of Thermoplastics by Extrusion Plastometer<sup>3</sup>

D 1600 Terminology for Abbreviated Terms Relating to Plastics<sup>3</sup>

D 1708 Test Method for Tensile Properties of Plastics By Use of Microtensile Specimens<sup>3</sup>

D 2863 Test Method for Measuring the Minimum Oxygen Concentration to Support Candle-Like Combustion of Plastics (Oxygen Index)<sup>4</sup>

D 3892 Practice for Packaging/Packing of Plastics<sup>4</sup>

D 4000 Classification System for Specifying Plastic Materials<sup>4</sup>

D 4591 Test Method for Determining Temperatures and Heats of Transitions of Fluoropolymer by Differential Scanning Calorimetry<sup>5</sup>

IEEE/ASTM SI 10 Standard for the Use of the International System of Units (SI): The Modern Metric System<sup>6</sup>

## 3. Terminology

3.1 *Definitions:* Definitions of terms used in this specification shall be in accordance with Terminology D 883.

3.1.1 *lot, n*—one production run or a uniform blend of two or more production runs.

3.2 *Abbreviations:* Abbreviations are in accordance with Terminology D 1600.

## 4. Classification

4.1 ECTFE materials are classified into groups according to their physical appearance. The groups are further divided into classes based on melt flow rate. These classes are subdivided into grades as shown in the Table E-CTFE.

An example of a material of this classification system is given as follows: ECTFE 01 1 1

where:

01 = ECTFE powder

1 = low melt flow

2 = properties in accordance with Table E-CTFE (Grade 1)

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.15 on Thermoplastic Materials (Section 20.15.12).

Current edition approved Dec. 10, 2000. Published March 2001. Originally published as D 3275 – 73. Last previous edition D 3275 – 97.

<sup>2</sup> Annual Book of ASTM Standards, Vol 10.01.

<sup>3</sup> Annual Book of ASTM Standards, Vol 08.01.

<sup>4</sup> Annual Book of ASTM Standards, Vol 08.02.

<sup>5</sup> Annual Book of ASTM Standards, Vol 08.03.

<sup>6</sup> Annual Book of ASTM Standards, Vol 14.02.

\*A Summary of Changes section appears at the end of this standard.

**TABLE E-CTFE**

Group	Class	Description	Grade	Melt Flow Rate, <sup>A</sup> g/10 min	Specific Gravity, <sup>B</sup> 23/23°C	Tensile Strength, <sup>C,D</sup> min, MPa	Elongation, <sup>D,E</sup> min, %	Melting Point, °C, <sup>F</sup> min	Oxygen Index, <sup>G</sup> min, %	Dielectric Constant, <sup>H</sup> max, 10 <sup>6</sup> Hz	Dissipation Factor, <sup>I</sup> max, 10 <sup>6</sup> Hz
01 powder	1	Low melt flow rate	1	0.05–1.50	1.65–1.71	40	200	240	60	2.6	0.015
	2	Medium melt flow rate	1	1.51–6.0	1.65–1.71	40	200	240	60	2.6	0.015
	3	High melt flow rate	1	6.1–25	1.65–1.71	40	200	240	60	2.6	0.015
	0	Other	0								
02 pellet	1	Low melt flow rate	1	0.05–1.50	1.65–1.71	40	200	240	60	2.6	0.015
	2	Medium melt flow rate	1	1.51–6.0	1.65–1.71	40	200	240	60	2.6	0.015
	3	High melt flow rate	1	6.1–25	1.65–1.71	40	200	240	60	2.6	0.015
	0	Other	0								
00	0	Other	0								

<sup>A</sup> See 11.2 for test method for above parameters.

<sup>B</sup> See 11.4 for test method for above parameters.

<sup>C</sup> See 11.5 for test method for above parameters.

<sup>D</sup> At 23 ± 2°C (73.4 ± 3.6°F).

<sup>E</sup> See 11.5 for test method for above parameters.

<sup>F</sup> See 11.3 for test method for above parameters.

<sup>G</sup> See 11.7 for test method for above parameters.

<sup>H</sup> See 11.6 for test method for above parameters.

<sup>I</sup> See 11.6 for test method for above parameters.

4.1.1 To facilitate incorporation of future material, the other category for Group (00), Class (0) and Grade (0) are shown in Table E-CTFE.

## 5. Ordering Information

5.1 The purchase order or inquiry for these materials shall state the classification callout. For example, D 3275 ECTFE 01 1 2.

5.2 Further definition, as may be required for the following, shall be on the basis of agreement between the seller and the purchaser:

5.2.1 Nominal Melt-Flow Rate.

## 6. General Requirements

6.1 The material covered by this specification shall conform to the requirements prescribed in Table E-CTFE when tested by the procedures specified herein.

## 7. Detail Requirements

7.1 Test specimens prepared in accordance with Section 10 shall conform to the requirements prescribed for the particular class.

## 8. Sampling

8.1 Sampling must be statistically adequate to satisfy the requirements of 12.4.

## 9. Number of Tests

9.1 One set of test specimens as prescribed in Section 11 shall be considered sufficient for testing each sample. The average result of the specimens tested shall conform to the requirements of this specification.

## 10. Specimen Preparation

10.1 *Test Specimens:*

10.1.1 Prepare test moldings 3.18 ± 0.3 mm (0.125 ± 0.012 in.) thick between two 0.38 to 0.51 mm (0.015 to 0.020 in.) thick chromium-plated ferrotype plates. Use a “picture frame” type compression molding chase with inner dimensions of 178 by 178 mm (7 by 7 in.) and having a thickness suitable to produce the required molded sheet. Use a charge of resin sufficient to provide the thickness sheet specified.

10.1.2 Place the mold chase on top of a chromium-plated ferrotype plate. Charge a quantity of resin sufficient to produce a 3.18 ± 0.30-mm (0.125 ± 0.012-in.) sheet in a diagonal pattern from corner to corner forming an “X” pattern. Place the other chromium-plated ferrotype plate on top of the resin charge and place the assembly in a compression molding press which has been heated to 264 ± 3°C (507 ± 5.4°F). Apply a pressure of 0.34 MPa (50 psi) and hold for 4 min. Increase pressure to 1.72 MPa (250 psi) and hold for 1 min followed by increasing the pressure to not less than 2.24 MPa (325 psi) and holding for 5 min. Remove the chase assembly from the press and immediately quench it in an ice-water bath, vigorously agitating the chase. Remove the ferrotype plates, keeping the chase and molded sheet in the ice water bath until quenching is complete.

## 11. Test Methods

11.1 *Conditioning:*

11.1.1 For tests of specific gravity, tensile properties, oxygen index, and electrical properties, condition the molded test specimens in accordance with Procedure A of Practice D 618, with the exception that only 4-h conditioning is required.

11.1.2 Conduct tests at the standard laboratory temperatures of 23 ± 2°C (73.4 ± 3.6°F) for determination of specific gravity, tensile properties, and electrical properties. Since the resin does not absorb water, the maintenance of constant humidity during testing is not necessary. Conduct tests for melt

flow rate, oxygen index, and melting endotherm under ordinary laboratory conditions.

11.2 *Melt Flow Rate*—Determine the melt flow rate in accordance with Test Method D 1238 modified by use of corrosion-resistant alloy for the barrel lining, orifice, and piston tip.

11.3 *Melting Endotherm Peak*—Determine the melting endotherm peak in accordance with Test Method D 4591. For instruments capable of digital data processing of the melting endotherm curve, the peak maximum, as determined by the point on the curve for which the tangent has zero slope, may be reported as the melting point. Additionally, the heat of fusion and recrystallization may be reported directly from the display of the data processing equipment provided that the instrument has been calibrated with a standard material as defined in Test Method D 4591.

11.3.1 Other thermal techniques, such as differential thermal analysis (DTA), capable of measuring the melting endotherm peak and giving equivalent results, may be used.

11.4 *Specific Gravity*—Cut two specimens from the compression molded sheet and test in accordance with Test Methods D 792.

11.5 *Tensile Properties*—Determine the tensile properties in accordance with Test Method D 638 and test specimen of Fig. 1 in this specification, except that the initial jaw separation shall be  $22.2 \pm 0.13$  mm ( $0.875 \pm 0.005$  in.), and the speed of testing shall be 51 mm/min (2 in./min). Clamp the specimens with essentially equal lengths in each jaw. Determine the elongation from the chart, expressing it as a percentage of the initial jaw separation. The test specimen and die identified in Test Method D 1708 may also be used.

11.6 *Dielectric Constant and Dissipation Factor*—Determine the dielectric constant and dissipation factor on three specimens, each 50.8 mm (2 in.) in diameter in accordance with Test Methods D 150. Testing shall be at 60 Hz and  $10^6$  Hz.

11.7 *Oxygen Index*—Determine the oxygen index in accordance with Test Method D 2863.

12. Inspection and Certification


12.1 Inspection and certification of the material supplied with reference to a specification based on this classification system shall be for conformance to the requirements specified herein.

12.2 Lot-acceptance shall be the basis on which acceptance or rejection of the lot is made. The lot-acceptance inspection shall consist of melt flow rate determination.


12.3 Periodic check inspection with reference to a specification based on this classification system shall consist of the tests for all requirements of the material under the specification. Inspection frequency shall be adequate to insure the material is certifiable in accordance with 12.4.

12.4 Certification shall be that the material was manufactured by a process in statistical control, sampled, tested, and inspected in accordance with this classification system, and that the average values for the lot meet the requirements of the specification (line callout).

12.5 A report of test results shall be furnished when requested. The report shall consist of results of the lot-acceptance inspection for the shipment and the results of the most recent periodic-check inspection.

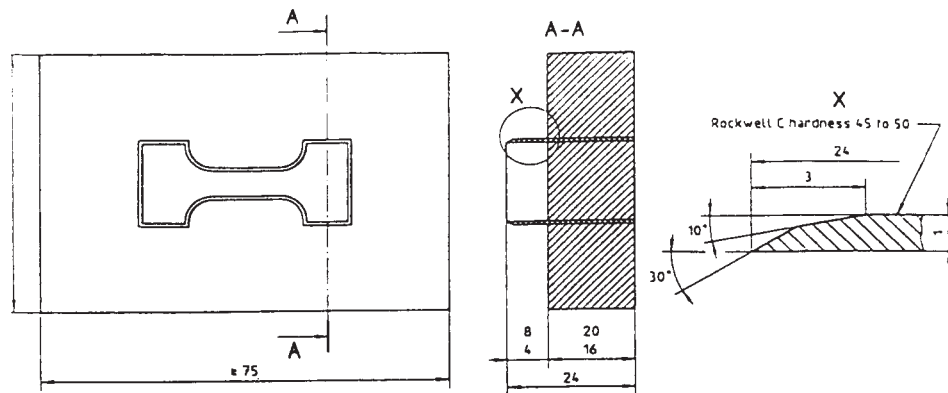

Steel-rule die  
(inside dimensions for die are the same as test specimen)  
Die to be sharpened on outside edge only (as shown in A-A)

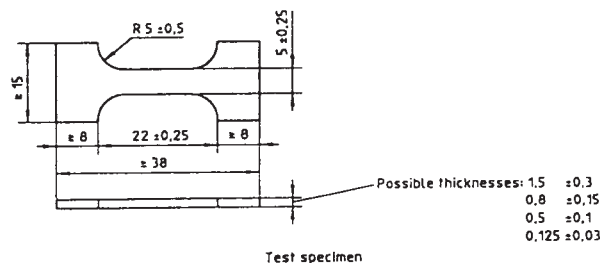

Test specimen

FIG. 1 Test Specimen and Die

### 13. Packaging and Package Marking

13.1 *Packaging*—The material shall be packaged in standard commercial containers so constructed as to ensure acceptance by common or other carriers for safe transportation to the point of delivery unless otherwise specified in the contract or order.

13.2 *Marking*—Shipping containers shall be marked with the name of the material, type, or melt index, and quantity therein.

13.3 All packing, packaging, and marking provisions of Practice D 3892 shall apply to this specification.

### 14. Keywords

14.1 chlorotrifluoroethylene copolymers; chlorotrifluoroethylene-ethylene copolymers; E-CTFE; extrusion material; fluoropolymer; fluoropolymers; melt flow; melt-processible fluoropolymer; molding material; powder coating; roto-lining; roto-molding

## APPENDIX

### (Nonmandatory Information)

#### X1. CLASSIFICATION

##### INTRODUCTION

This information is included to enable an easy comparison of the previous classification system (D 3275–97) and the current Classification D 4000 format system. This appendix will be deleted as part of the next revision.

X1.1 This specification covers three types of E-CTFE-fluoroplastic supplied in pellet or powder forms for molding, extrusion, and coatings:

- X1.1.1 *Type I*—Low melt flow rate.
- X1.1.2 *Type II*—Medium melt flow rate.
- X1.1.3 *Type III*—High melt flow rate.

X1.2 A one-line system may be used to specify materials covered by this specification. The system uses predefined cells to refer to specific aspects of this specification, as illustrated below.

Specification	
Standard Number	Type
Block	:
:	:
Example: Specification D 3275 – 97,	I

For this example, the line callout would be Specification D 3275 and would specify a low melt flow rate extrusion and molding grade of E-CTFE that has all of the properties listed for that Type in the appropriate tables, or both, in the specification identified. A comma is used as the separator between the Standard Number and the Type.

**TABLE X1.1 Detail Requirements for Test on Molding Materials**

	Type I	Type II	Type III
Melt flow rate, g/10 min:			
min	0.05	0.85	4.1
max	0.84	4.0	25
Melting endotherm peak, min, °C	240 <sup>A</sup>	240 <sup>A</sup>	240 <sup>A</sup>

<sup>A</sup> If the melting peak endotherm is determined by a digital method that calculates the peak by determining when the tangent has zero slope, as described in 11.3, the result can be lower than when the method defined in Test Method D 4591 is used. For this reason, the minimum melting point specification must be reduced to 239°C when the former approach is used.

**TABLE X1.2 Detail Requirements for Molded Test Specimens of Types I, II, and III Resins**

Specific gravity, 23/23°C (73.4/73.4°F):	
min	1.65
max	1.71
Ultimate Tensile strength, 23°C (73.4°F), min:	
MPa	41.4
psi	6000
Ultimate Elongation, 23°C (73.4°F), min, %:	200
Oxygen index, min, %:	52
Dielectric constant, max:	
106 Hz	2.6
Dissipation factor, max:	
10 <sup>6</sup> Hz	0.015

### SUMMARY OF CHANGES

This section identifies the location of selected changes to this classification. For the convenience of the user, Committee D20 has highlighted those changes that may impact the use of this classification. This section may also include descriptions of the changes or reasons for the changes, or both.

*D 3275 – 00:*

- (1) Changed title from “Standard Specification” to “Standard Classification.”
- (2) Deleted Practice D 1898 from Section 2.
- (3) Replaced Practice E 380 with IEEE/ASTM SI 10 in 1.2 and Section 2.
- (4) Deleted Test Method D 1505 from Section 2 due to cancer causing nature of solvents employed.
- (5) Added new definition for *lot* (3.1.1).
- (6) Added abbreviations section (3.2).

- (7) Deleted all references to Table 2 from document.
- (8) In Section 4, classification system changed to D 4000 format and old system put in Appendix X1 for reference for less than or equal to five years.
- (9) Changed melt flow rates from 0.05–0.84, 0.85–4.0, and 4.1–25 to 0.05–1.5, 1.51–6.0, and 6.1–25 for low, medium, and high melt flow materials.
- (10) Changed oxygen index from 52 min to 60 min.
- (11) Added new Section 12, Inspection and Certification.

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*