



Standard Test Method for Fracture Strength in Cleavage of Adhesives in Bonded Metal Joints¹

This standard is issued under the fixed designation D 3433; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method (**1, 2, 5, 6, 9**)² covers the determination of fracture strength in cleavage of adhesives when tested on standard specimens and under specified conditions of preparation and testing (Note 1).

1.2 This test method is useful in that it can be used to develop design parameters for bonded assemblies.

NOTE 1—While this test method is intended for use in metal-to-metal applications it may be used for measuring fracture properties of adhesives using plastic adherends, provided consideration is given to the thickness and rigidity of the plastic adherends.

1.3 The values stated in SI units are considered to be the standard. Values in parentheses are for information purposes.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

- A 167 Specification for Stainless and Heat-Resisting Chromium-Nickel Steel Plate, Sheet, and Strip³
- A 366/A366M Specification for Steel, Sheet, Carbon, Cold-Rolled, Commercial Quality³
- B 36 Specification for Brass Plate, Sheet, Strip, and Rolled Bar⁴
- B 152 Specification for Copper Sheet, Strip, Plate, and Rolled Bar⁴
- B 209 Specification for Aluminum and Aluminum-Alloy Sheet and Plate⁵
- B 265 Specification for Titanium and Titanium Alloy Strip, Sheet, and Plate⁶

¹ This test method is under the jurisdiction of ASTM Committee D-14 on Adhesives and is the direct responsibility of Subcommittee D14.80 on Metal Bonding Adhesives.

Current edition approved May 10, 1999. Published August 1999. Originally published as D 3433 – 75. Last previous edition D 3433 – 93.

² The boldface numbers in parentheses refer to the references at the end of this test method.

³ *Annual Book of ASTM Standards*, Vol 01.03.

⁴ *Annual Book of ASTM Standards*, Vol 02.01.

⁵ *Annual Book of ASTM Standards*, Vol 02.02.

⁶ *Annual Book of ASTM Standards*, Vol 02.04.

D 907 Terminology of Adhesives⁷

E 4 Practices for Force Verification of Testing Machines⁸

E 399 Test Method for Plane-Strain Fracture Toughness of Metallic Materials⁸

3. Terminology

3.1 *Definitions*: Many of the terms used in this test method are defined in Terminology D 907.

3.2 *Definitions of Terms Specific to This Standard*:

3.2.1 *crack-extension force, G*,—the system isolated (fixed load-displacement) loss of stress field energy for an infinitesimal increase, dA , of separational area. In equation form,

$$GdA = -dU_T \quad (1)$$

where U_T = total elastic energy in the system (component or test specimen). In the test specimens of this method, the crack front is nearly straight through the specimen thickness, B , so that $dA = B da$, where da is an infinitesimal forward motion of the leading edge of the crack. Completely linear-elastic behavior is assumed in the calculations (See Annex A1) of G used in this method, an allowable assumption when the zone of nonlinear deformation in the adhesive is small relative to specimen dimensions and crack size.

3.2.1.1 When the shear stress on the plane of crack and forward to its leading edge is zero, the stress state is termed “opening mode.” The symbol for an opening mode G is G_I for plane-strain and G_{I1} when the connotation of plane-strain is not wanted.

3.2.2 *opening mode fracture toughness, G_{Ic}* —the value of G just prior to onset of rapid fracturing when G is increasing with time.

3.2.3 *opening mode crack arrest toughness, G_{Ia}* —the value of G just after arrest of a run-arrest segment of crack extension.

3.2.3.1 It is assumed that the dimensions of the part containing the crack are large compared to the run-arrest segment which precedes crack arrest and that the quasi-static stress field enclosing the crack tip just after crack arrest can be assumed in calculating G_{Ia} .

4. Summary of Test Method

4.1 This test method involves cleavage testing bonded specimens such that a crack is made to extend by a tensile force

⁷ *Annual Book of ASTM Standards*, Vol 15.06.

⁸ *Annual Book of ASTM Standards*, Vol 03.01.

acting in a direction normal to the crack surface.

4.2 Load versus load-displacement across the bondline is recorded autographically. The G_{1c} and G_{1a} values are calculated from this load by equations that have been established on the basis of elastic stress analysis of specimens of the type described below. The validity of the determination of G_{1c} and G_{1a} values by this test method depends upon the establishment of a sharp-crack condition in the bondline in a specimen of adequate size. This test method will measure the fracture strength of a bonded joint which is influenced by adherend surface condition, adhesive, adhesive-adherend interactions, primers, adhesive-supporting scrim, etc., and in which of the above possible areas the crack grows.

5. Significance and Use

NOTE 2—Crack growth in adhesive bond specimens can proceed in two ways: (1) by a slow-stable extension where the crack velocity is dictated by the crosshead rate or (2) by a run-arrest extension where the stationary crack abruptly jumps ahead outrunning the crosshead-predicted rate. The first type of crack extension is denoted flat; the second type peaked because of the appearance of the autographic record. The flat behavior is characteristic of adhesives or test temperatures, or both, for these adhesives where there is no difference between initiation, G_{1c} , and arrest, G_{1a} . For example, the rubber modified film adhesives tested above -17.8°C (0°F) all exhibit flat autographic records. Peaked curves are exhibited for all modified materials tested below -73°C (-100°F) and in general for unmodified epoxies.

It should be noted that both peaked and flat behaviors are determined from a crack-length-independent specimen. For other specimens or structures where G increases with a at constant load the onset of crack growth would result in rapid complete fracturing whatever the adhesive characteristics.

5.1 The property G_{1c} (and G_{1a} if relevant) determined by this test method characterizes the resistance of a material to slow-stable or run-arrest fracturing in a neutral environment in the presence of a sharp crack under severe tensile constraint, such that the state of stress near the crack front approaches tritensile plane strain, and the crack-tip plastic region is small compared with the crack size and specimen dimensions in the constraint direction. It has not been proven that tough adhesive systems fully meet this criteria. Therefore, data developed using equations based on this assumption may not represent plane-strain fracture values. Comparison of fracture toughness between adhesive systems widely different in brittleness or toughness should take this into consideration. In general, systems of similar type toughness (3, 4, 7, 8, 10) can be compared as can the effect of environment on toughness of a single system. A G_{1c} value is believed to represent a lower limiting value of fracture toughness for a given temperature, strain rate, and adhesive condition as defined by manufacturing variables. This value may be used to estimate the relation between failure stress and defect size for a material in service wherein the conditions of high constraint described above would be expected. Background information concerning the basis for development of this test method in terms of linear elastic fracture mechanics may be found in Refs (6) and (7).

5.1.1 Cyclic loads can cause crack extension at G_1 values less than G_{1c} value. Furthermore, progressive stable crack extension under cyclic or sustained load may be promoted by the presence of certain environments. Therefore, application of G_{1c} in the design of service components should be made with

awareness of the G increase for a prior crack which may occur in service due to slow-stable crack-extension.

5.2 This test method can serve the following purposes:

5.2.1 In research and development to establish, in quantitative terms, significant to service performance, the effects of adhesive composition, primers, adherend surface treatments, supporting adhesive carriers (scrim), processing variables, and environmental effects.

5.2.2 In service evaluation to establish the suitability of an adhesive system for a specific application for which the stress conditions are prescribed and for which maximum flaw sizes can be established with confidence.

5.2.3 For specifications of acceptance and manufacturing quality control, but only when there is a sound basis for specification of minimum G_{1c} values. The specification of G_{1c} values in relation to a particular application should signify that a fracture control study has been conducted on the component in relation to the expected history of loading and environment, and in relation to the sensitivity and reliability of the crack detection procedures that are to be applied prior to service and subsequently during the anticipated life.

6. Apparatus

6.1 *Testing Machine*, conforming to the requirements of Practices E 4. Select the testing machine such that the cracking load of the specimens falls between 15 and 85 % of the full-scale capacity and that is provided with a suitable pair of self-aligning pinned fixtures to hold the specimen.

6.2 Ensure that the pinned fixtures and attachments are constructed such that they will move into alignment with the test specimen as soon as the load is applied.

6.3 For a discussion of the calculation of separation rates see Annex A1.

7. Test Specimens

7.1 *Flat Adherend*, conforming to the form and dimensions shown in Fig. 1, cut from test joints as in Fig. 2, prepared as prescribed in Section 8.

7.2 *Contoured Double-Cantilever Beam (CDCB)*, conforming to the form and dimensions shown in Fig. 3.

7.3 The following grades of metals are suggested for the test specimens (Note 3):

Metal	ASTM Designation
Brass	B 36, Alloy 260 (6), quarter hard temper
Copper	B 152, cold rolled, Type 110, hard temper
Aluminum	B 209, Alclad 2024, T3 temper, mill finish
Steel	A 366, regular matte finish
Corrosion-resisting steel	A 167, Type 304, No. 2B finish
Titanium	B 265, Grade 3

7.4 Test at least twelve specimens, representing at least four different joints.

NOTE 3—Since it is unacceptable to exceed the yield point of the metal in flexure during test, the permissible thickness of the specimen will vary with type of metal, and the general level of strength of the adhesive being investigated. The minimum permissible thickness in a uniform symmetrical adherend may be computed from the following relationship:

$$h = \sqrt{\frac{6Ta}{BF_y}} \quad (2)$$

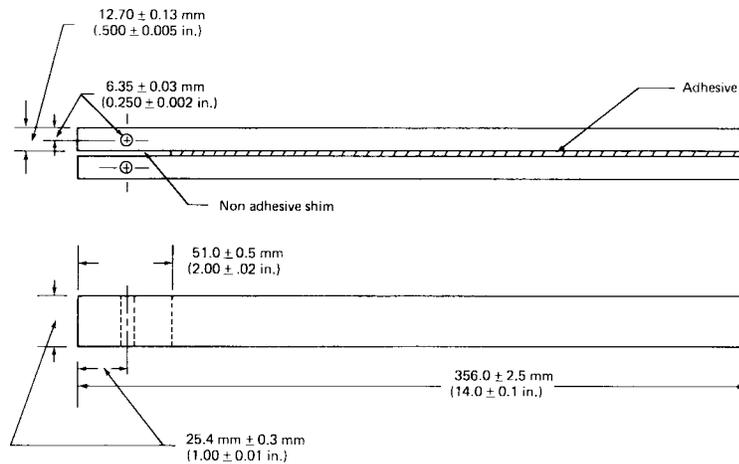


FIG. 1 Flat Adherend Specimen

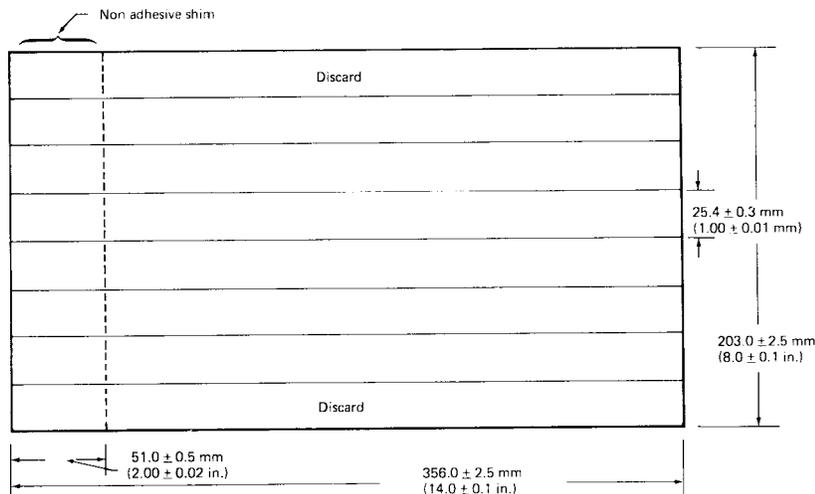


FIG. 2 Test Joint

where:

- h = thickness of metal normal to plane of bonding, mm (or in.),
- F_{ty} = tensile yield point of metal (or the stress at proportional limit) MPa (or psi),
- T = 150 % of the maximum load to start the crack in the adhesive bond, N (or lbf),
- a = crack length at maximum load, mm (or in.), and
- B = bond width, mm (or in.).

8. Preparation of Test Joints

8.1 Cut sheets of the metals or contoured adherends prescribed in 7.1-7.3 and to recommended size (Figs. 2 and 3). All edges of the metal panels and specimens must be flat, free of burrs, and smooth (4.1- μm (160- $\mu\text{in.}$) maximum) before the panels are surface-treated and bonded. Clean, treat, and dry the sheets or contoured adherends carefully, in accordance with the procedure prescribed by the manufacturer of the adhesive. Prepare and apply the adhesive in accordance with the recommendations of the manufacturer of the adhesive. Apply the adhesive to the faying surface of one or both metal sheets. Then assemble the sheets, faying surface to faying surface in pairs, and allow the adhesive to cure under conditions prescribed by the manufacturer of the adhesive.

8.2 It is recommended that each "flat adherend" test joint be made with sufficient area to provide at least five test specimens.

9. Preparation of Test Specimens

9.1 For flat adherend test specimens, trim joint area in accordance with Fig. 2. Then cut test specimens, as shown in Fig. 1, from the joints, Fig. 2 (Note 4). Then cut holes for load pins as shown in Fig. 1.

9.2 Contoured double-cantilever specimens are ready for test as bonded.

NOTE 4—Do not use lubricants or oils during the cutting process. For aluminum it is suggested that the specimens be rough cut 3.2 mm (1/8 in.) over-size using a four-pitch band saw traveling at approximately 4.2 m/s (800 ft/min) followed by finish dimensioning to a 1-in. wide 3.2- μm (125- $\mu\text{in.}$) surface using a five-blade 15-deg carbide fly cutter at 1115 rpm and 0.015 to 0.035-m/s (3 to 7-in./min) feed rate.

10. Procedure

10.1 Test specimens, prepared as prescribed in Section 8, in an atmosphere maintained at $50 \pm 4\%$ relative humidity and $23 \pm 1^\circ\text{C}$ ($73.4 \pm 1.8^\circ\text{F}$). Tests at other than ambient temperature may be run if desired. It is suggested that specimens be conditioned for a minimum of 10 min and a maximum of 30 min at the temperature of test to assure equilibrium. The manufacturer of the adhesive may, however, prescribe a definite period of conditioning under specific conditions before testing.

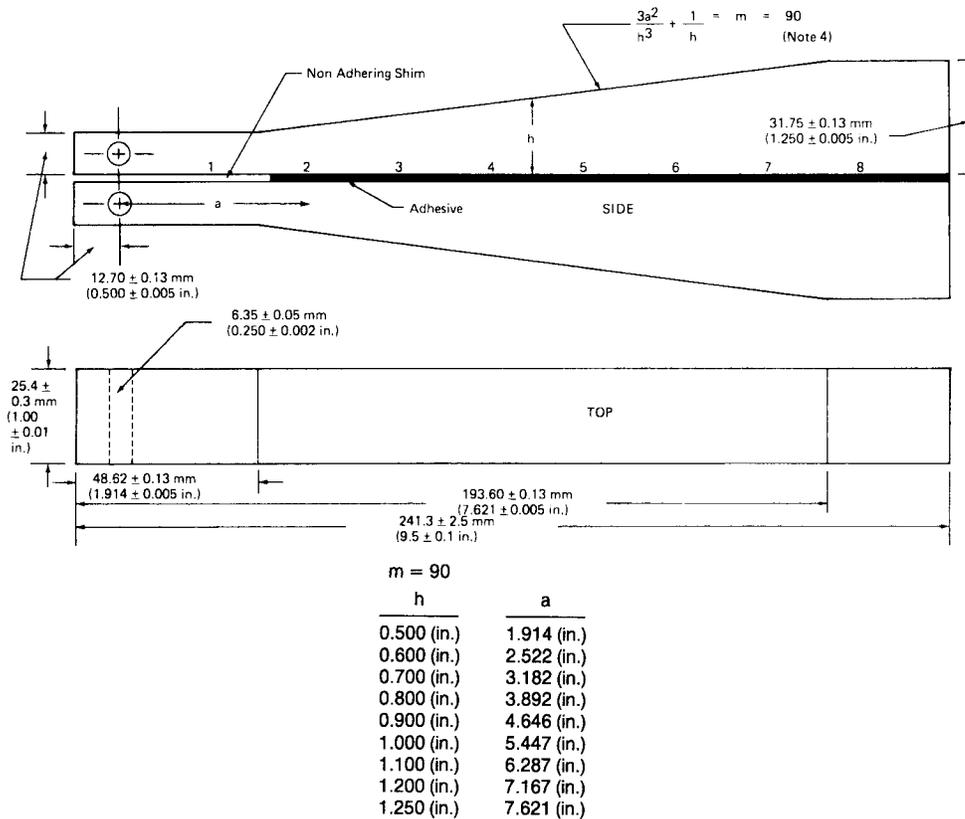


FIG. 3 Contoured Double-Cantilever Beam Specimen

10.2 Determine the following test specimen dimensions.

10.2.1 Distance from center of 6.4-mm (0.25-in.) inside-diameter pin holes to close end of specimen.

10.2.2 Width of test specimen, b .

10.2.3 Thickness of test specimen 127 mm (5 in.) from pin end and 227 mm (9 in.) from pin end.

10.2.4 Bond line thickness 125 mm (5 in.) from pin end and 227 mm (9 in.) from pin end.

10.3 Load the specimen in the test machine and pin in position using the 6.4-mm (0.25-in.) inside-diameter pin holes. Balance the recorder or chart, or both. Set the test machine at a crosshead separation rate Δ chosen to keep time-to-fracture in the order of 1 min, see 6.1 and Annex A1. For example, 2 mm/min (0.08 in./min) gives fracture in 1 min for a CDCB 1/2-in. wide $m = 90$ -in.⁻¹ aluminum adherend specimen having a 3-in. long starter crack.

10.3.1 The chart recording should be such that maximum load occurs on the record and that at least 13 mm (1/2 in.) of motion is represented on the abscissa (Δ) for each 100 mm (4 in.) of ordinate motion (P). For load-time records a chart speed rate should be used such that the slope of the load versus time record is similar to that specified for load versus load-displacement (for example, 5 mm/min (0.2 in./mm)).

10.4 Apply load to specimen until Point A is reached. (See Point A, Fig. 4 for flat adherend and Fig. 5, Point A for contoured double-cantilever specimen.) Point A is the load at which the crack begins to grow rapidly. Then stop loading and follow crack growth curve on the chart. When the load has leveled off at an approximate constant value (the crack has stopped growing), determine and record the following values:

Load versus Time chart

(For 5 determinations on a single test specimen)

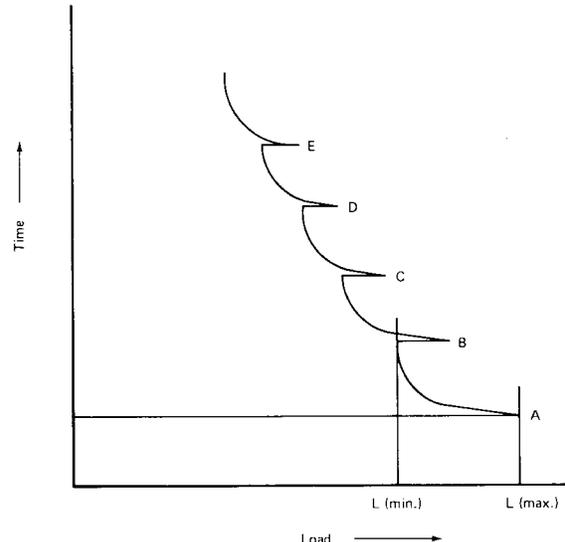


FIG. 4 Typical Flat Adherend Test

10.4.1 Load to start crack, L (max), N (or lbf),

10.4.2 Load when crack stops, L (min), N (or lbf), and

10.4.3 Distance from loading end of specimen to the stationary crack tip in millimetres (or inches).

10.5 Repeat 10.4 to yield five determinations on each specimen.

Load – Crack Chart
(For 6 determinations on a single test specimen)

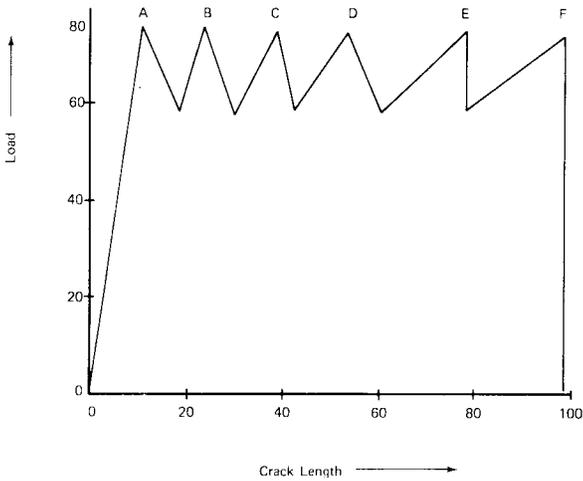


FIG. 5 Typical Contoured Double-Cantilever Beam Test

11. Calculation

11.1 Flat Adherend Specimen:

11.1.1 Calculate the fracture toughness, G_{1c} (from load to start crack), in joules per square metre or pounds-force per inch as follows:

$$G_{1c} = \frac{[4L^2(\max)][3a^2 + h^2]}{[EB^2h^3]} \quad (3)$$

11.1.2 Calculate fracture toughness, G_{1a} (from arrest load), as follows:

$$G_{1a} = \frac{[4L^2(\min)][3a^2 + h^2]}{[EB^2h^3]} \quad (4)$$

where:

- $L(\max)$ = load to start crack, N (or lb),
- $L(\min)$ = load at which crack stops growing, N (or lb),
- E = tensile modulus of adherend, MPa (or psi),
- B = specimen width, mm (or in.),
- a = crack length, mm (or in.) (= distance from crack tip to pin hole centers), and
- h = thickness of adherend, normal to plane of bonding mm (or in.) (= 12.7 mm (0.50 in.) unless otherwise specified).

11.2 Contoured Double-Cantilever Specimen:

11.2.1 Calculate the fracture toughness, G_{1c} (from load to start crack), in joules per square metre or pounds-force per inch, as follows:

$$G_{1c} = \frac{[4L^2(\max)](m)}{[EB^2]} \quad (5)$$

11.2.2 Calculate the fracture toughness, G_{1a} (from arrest load), as follows:

$$G_{1a} = \frac{[4L^2(\min)](m)}{[EB^2]} \quad (6)$$

where:

- a = crack length, mm (or in.) (= distance from crack tip to pin hole centers),
- h = thickness of adherend, normal to plane of bonding, mm (or in.),
- m = $3a^2/h^3 + 1/h$, (Note 3) (Note 5),
- $L(\max)$ = load to start crack, N (or lbf),
- $L(\min)$ = load at which crack stops growing, N (or lbf),
- E = tensile modulus of adherend, MPa (or psi),
- B = specimen width, mm (or in.),

NOTE 5—The purpose of the contoured double-cantilever specimen is to make the measurement of fracture toughness G_1 independent of crack length a .

To develop a linear compliance specimen, its height is varied so that the quantity $3a^2/h^3 + 1/h$ is constant. Hence,

$$\frac{3a^2}{h^3} + \frac{1}{h} = m \quad (7)$$

There are, of course, any number of m values that can be used in designing a specimen. A convenient contour for testing adhesives is $m = 90 \text{ in.}^{-1}$, as shown in Fig. 3. The very high m number or low-taper angle would cause a large bending stress on the plane of the crack if the specimen were monolithic. Because of the low modulus of the adhesives compared with that of the adherends, these bending stresses are not significant. If bulk specimens of the adhesive materials are to be tested, the bending stresses tend to cause one or the other arm to break off. This problem is minimized by using lower m numbers, that is, by making the beams stiffer, and adding side grooves to the specimens to direct the crack in the desired plane of extension. When the specimens are made stiffer, the description of m as $3a^2/h^3 + 1/h$ is satisfactory for designing linear compliance specimens but cannot be used to calculate G_{1c} because the assumptions used in beam theory become increasingly invalid as the beam height to length ratio increases. In place of m an experimental value determined from compliance calibrations and designated as m' is required. Hence, the toughness for monolithic specimens having low m values is defined as

$$G_{1c} = \frac{L^2(\max)[8][m']}{2B_n Eb} \quad (8)$$

where:

- B_n = specimen width at crack plane, and
- b = gross specimen width.

12. Report

12.1 Report the following information:

12.1.1 Complete identification of the adhesive tested, including type, source, date manufactured, manufacturers code number, form, etc.,

12.1.2 Complete identification of the metal used, its thickness, and the method of cleaning and preparing its surfaces prior to bonding,

12.1.3 Application and bonding conditions used in preparing the specimens,

12.1.4 Conditioning procedure used for specimens prior to testing,

12.1.5 Test temperature,

12.1.6 Loading rate used,

12.1.7 Time-to-fracture,

12.1.8 Chart speed used,

12.1.9 Number of specimens tested,

12.1.10 Number of joints represented,

12.1.11 Bondline thickness (Note 4),

12.1.12 Individual G_{1c} and G_{1a} (fracture toughness to start

crack and fracture toughness from arrest load) values for each specimen,

12.1.13 Maximum, minimum, and average values for G_{1c} and G_{1a} , and

12.1.14 The nature of the failure, including the average estimated percentages of failure in the cohesion of the adhesive, contact failure, voids, and apparent adhesion to the metal.

NOTE 6—Report the average thickness of adhesive layer after formation of the joint within 0.01 mm (0.0005 in.). Describe the method of obtaining the thickness of the adhesive layer including procedure, location of measurements, and range of measurements.

13. Precision and Bias

13.1 The following data should be used for judging the acceptability of results (95 % confidence limits) (Note 7):

13.1.1 *Repeatability*— Duplicate test results by an indi-

vidual should be considered suspect if they differ by more than 10 %.

13.1.2 *Reproducibility*— The average result reported by one laboratory should be considered suspect if it differs from that of another laboratory by more than 10 %.

NOTE 7—These precision data are approximations based on limited data, but they provide a reasonable basis for judging the significance of results. Care must be taken to control variation in bondline thickness and to measure the crack length accurately. The ability to measure the crack tip and its geometry as well as actual variation in the material properties of some adhesive may result in performance which will have greater scatter.

14. Keywords

14.1 adhesive; bonded joint; cleavage; double-cantilever beam; fracture strength

ANNEX

(Mandatory Information)

A1. CALCULATION OF SEPARATION RATES

A1.1 Fracture tests are generally designed so that the onset of crack extension occurs in about 1 min from the time monotonically increasing loading begins. Due to compliance and compliance change differences for different specimen geometries specific ranges of separation rate are required to conform this time to fracture specification. Thus, the calculation of separation rates for a particular test specimen shall be done using the following expressions. For contoured double-cantilever beams (CDCB):

$$3200 CB/2 \sqrt{m'} < \dot{\Delta} < 16\ 000 CB/2 \sqrt{m'} \quad (\text{A1.1})$$

where:

Δ = displacement of the load (load-displacement), mm (or in.),

$\dot{\Delta}$ = load-displacement rate, mm (or in.)/min,

B = specimen width,

m' = defined in Section 11,

C = specimen compliance, MPa (or psi); a function of crack length, namely:

$$C = 8/EB [(3 (a_o)^2/h^3 + 1/h) + m' (a - a_o)]$$

E = tensile modulus (defined in Section 11),

a = crack length, mm (or in.) (defined in Section 11),

a_o = length of constant-height section of the front part of the specimen from the center-line of the loading holes to the point at which the contoured section begins, and

h = adherend thickness, mm (or in.) (defined in Section 11).

NOTE A1.1—The constants 3200 and 16 000 are in units of psi $\sqrt{\text{in.}}$ and require all units in the equation to be in similar units. If MKS, metric conversion is desirable 3200 and 16 000 psi $\sqrt{\text{in.}}$ are 3.51 and 17.57 MPa-m^{-3/2}.

A1.1.1 For example, for 1/2-in. thick, 1/2-in. wide aluminum $m' = 90\text{-in.}^{-1}$ adherends, the expression for $\dot{\Delta}$ and C becomes

$$84C < \dot{\Delta} < 416C$$

$$C = 100/10^6 + 144/10^6 (a - 1.625) \quad (\text{A1.2})$$

A1.1.2 For a crack length of 3 in. a rate of 0.08 in./min will cause crack growth to occur in 1 min if G_{Ic} is 10 lb/in. For a 3-in. long crack,

$$0.025 < \dot{\Delta} < 0.124 \quad (\text{A1.3})$$

and the value of 0.08 is within the range specified. This expression for $\dot{\Delta}$ in terms of C will give fracture times in the order of 1 min for G_{Ic} values between 1 and 25. ($\dot{\Delta}$ should be selected for a given adhesive toughness to give time-to-fracture values close to 1 min.)

A1.1.3 The value of $\dot{\Delta}$ should be increased periodically as the crack extends such that it conforms to the expression. If the crack were to be at 6 in.:

$$0.053 < \dot{\Delta} < 0.26 \quad (\text{A1.4})$$

The value of 0.08 in./min would still be within the above range; however, fracture times would be increased to 2 min ($G_{Ic} = 10$ lb/in.). This in itself is not considered a violation of specifications, but if fracture times were to be shortened to 1 min, $\dot{\Delta}$ would have to be increased to 0.17 in./min.

A1.1.4 In practice, the crack would be run for some distance, for example 2 in., and the loading rate increased to reduce the fracture time to an acceptable value.

A1.1.5 The calculation of $\dot{\Delta}$ for uniform double-cantilever beam specimens can be done in much the same manner; for example:

$$\frac{3200 CB}{2 \sqrt{\frac{3(a+0.6h)^2}{h^2} + \frac{1}{h}}} < \dot{\Delta} < \frac{16\ 000 CB}{2 \sqrt{\frac{3(a+0.6h)^2}{h^2} + \frac{1}{h}}} \quad (\text{A1.5})$$

$$C = 8/EB \left(\frac{(a + 0.6h)^3}{h^3} + \frac{a}{h} \right)$$

A1.1.6 For a 3-in. long crack in a 1/2-in. thick 1/2-in. wide aluminum adherend specimen:

$$0.023 < \dot{\Delta} < 0.116 \quad (\text{A1.6})$$

In order to keep $\dot{\Delta}$ within the tolerance limits crack length would have to be monitored which, of course, would have to be done to determine initial values of G .

A1.2 It should also be noted that $\dot{\Delta}$, the load-displacement, is not identical with jaw separation, although for low loads using a relatively stiff testing machine they will be close. For those tests where it is determined that there is a substantial difference between $\dot{\Delta}$ and jaw separation rate the jaw separation rate should be increased to conform with time-to-fracture requirements. Subsequent tests should be made using whatever correction factor is determined for the particular test machine.

REFERENCES

- (1) Ripling, E. J., Mostovoy, S. and Patrick, R. L., "Application of Fracture Mechanics to Adhesive Joints," *ASTM STP 360*, ASTM, 1963.
- (2) Ripling, E. J., Mostovoy, S., and Patrick, R. L., "Measuring Fracture Toughness of Adhesive Joints," *Materials, Research, and Standards*, ASTM, Vol 64, No. 3, 1964.
- (3) Mostovoy, S., and Ripling, E. J., "Fracture Toughness of an Epoxy System," *Journal of Applied Polymer Science*, Vol 10, 1966, pp. 1351-1371.
- (4) Mostovoy, S., and Ripling, E. J., "Influence of Water on Stress Corrosion Cracking of Epoxy Bonds," *Journal of Applied Polymer Science*, Vol 13, 1969, pp. 1082-1111.
- (5) Mostovoy, S., Bersch, C. F., and Ripling, E. J., "Fracture Toughness of Adhesive Joints," *Journal of Adhesion*, Vol 3, 1971, pp. 125-144.
- (6) Ripling, E. J., Corten, H. T., and Mostovoy, S., "Fracture Mechanics: A Tool for Evaluating Structural Adhesives," *Journal of Adhesion*, Vol 3, 1971, pp. 107-123. (Also published in *SAMPE Journal*, 1970).
- (7) Ripling, E. J., Bersch, C., and Mostovoy, S., "Stress Corrosion Cracking of Adhesive Joints," *Journal of Adhesion*, Vol 3, 1971, pp. 145-163. (Also published in *SAMPE Journal*, 1970).
- (8) Mostovoy, S., and Ripling, E. J., "The Fracture Toughness and Stress Corrosion Cracking Characteristics of an Adhesive," *Journal of Applied Polymer Science*, Vol 15, 1971, pp. 641-659. (Also published in *SAMPE Journal*, 1970.)
- (9) Mostovoy, S., and Ripling, E. J. "Effect of Joint Geometry on the Toughness of Epoxy Adhesives," *Journal of Applied Polymer Science*, Vol 15, 1971, pp. 661-673. (Also published *SAMPE Journal*, 1970.)
- (10) Mostovoy, S., and Ripling, E. J., "Effect of Temperature on the Fracture Toughness and Stress Corrosion Cracking of Adhesives," *Applied Polymer Symposium No. 19*, 1972, pp. 395-408.

The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.

This standard is copyrighted by ASTM, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (<http://www.astm.org>).