



# Standard Test Method for Deposition Tendencies of Liquids in Thin Films and Vapors<sup>1</sup>

This standard is issued under the fixed designation D 3711; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

<sup>ε1</sup> NOTE—Warning notes were placed in the text editorially in November 2000.

## 1. Scope

1.1 This test method covers the determination of the tendency of liquids in thin films and of vapors to form deposits on metal surfaces. The test method applies to both petroleum-based and synthetic lubricants, hydraulic fluids, heat-transfer fluids, and related materials.<sup>2</sup>

1.2 The values stated in SI units are to be regarded as the standard. In cases where materials, products, or equipment are available in inch-pound units only, SI units are omitted.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* For specific hazard statements, see Section 7.

## 2. Referenced Documents

### 2.1 ASTM Standards:

D 216 Method for Distillation of Natural Gasoline<sup>3</sup>

D 323 Test Method for Vapor Pressure of Petroleum Products (Reid Method)<sup>4</sup>

D 4057 Practice for Manual Sampling of Petroleum and Petroleum Products<sup>5</sup>

D 4177 Practice for Automatic Sampling of Petroleum and Petroleum Products<sup>5</sup>

E 230 Specification Temperature-Electromotive Force (EMF) Tables for Standardized Thermocouples<sup>6</sup>

### 2.2 ANSI Standard:

C 96.1 Temperature Measurement Thermocouples.<sup>7</sup>

<sup>1</sup>This test method is under the jurisdiction of ASTM Committee D02 on Petroleum Products and Lubricants and is the direct responsibility of Subcommittee D02.11 on Engineering Science of High Performance Fluids and Solids.

Current edition approved Jan. 15, 1995. Published March 1995. Originally published as D 3711 – 78. Last previous edition D 3711 – 93.

<sup>2</sup>United States Patent 2,669,865. Joseph Cole and John Krawetz.

<sup>3</sup>Discontinued—see *1987 Annual Book of ASTM Standards*, Vol 05.01.

<sup>4</sup>*Annual Book of ASTM Standards*, Vol 05.01.

<sup>5</sup>*Annual Book of ASTM Standards*, Vol 05.02.

<sup>6</sup>*Annual Book of ASTM Standards*, Vol 14.03.

<sup>7</sup>Available from American National Standards Institute, 11 W. 42nd St., 13th Floor, New York, NY 10036.

## 3. Terminology

### 3.1 Definitions of Terms Specific to This Standard:

3.1.1 *deposit tendency, n*—the deposition tendency of a thin film or vapor is an index of the propensity of a material to form carbonaceous residues on hot surfaces in contact with the liquid or vapor phase of the sample.

## 4. Summary of Test Method

4.1 The test specimen is allowed to flow slowly in a thin film over a steel test specimen in a constant-temperature chamber (furnace liner). Circulation of the sample from the sump to the heated surface and back to the sump is accomplished by means of a peristaltic pump. After the prescribed test period, the steel test specimen is removed from the apparatus and evaluated. The masses of deposits remaining after washing with pentane, after washing with chloroform, and after wiping with a paper tissue are reported.

4.2 An optional procedure (see Annex A1) provides a method for the determination of the tendency of sample vapors to form deposits on heated surfaces. A second test specimen is placed in the vapor space over a thin flowing film of the liquid in a constant-temperature chamber (furnace liner). After circulation of the test liquid for a specified time the deposits on the test specimen exposed to the liquid and the vapor phases are measured in the manner described in 4.1.


## 5. Significance and Use

5.1 The test method shall measure the deposit formation tendencies of liquids on steel surfaces in air at 101.3 KPa (1-atm) pressure. Other surfaces and other atmospheric media may be substituted for steel and air at 1 atm provided that the substitution is noted in the test report.

## 6. Apparatus

6.1 *Tube Furnace*, with heating chamber 305 mm (12 in.) long by 35 mm (1 $\frac{3}{8}$  in.) in diameter<sup>8</sup> (see Fig. 1).

<sup>8</sup>Type FD303A combustion furnace manufactured by Hoskins Manufacturing Co., Detroit, MI 48232, has been found satisfactory.

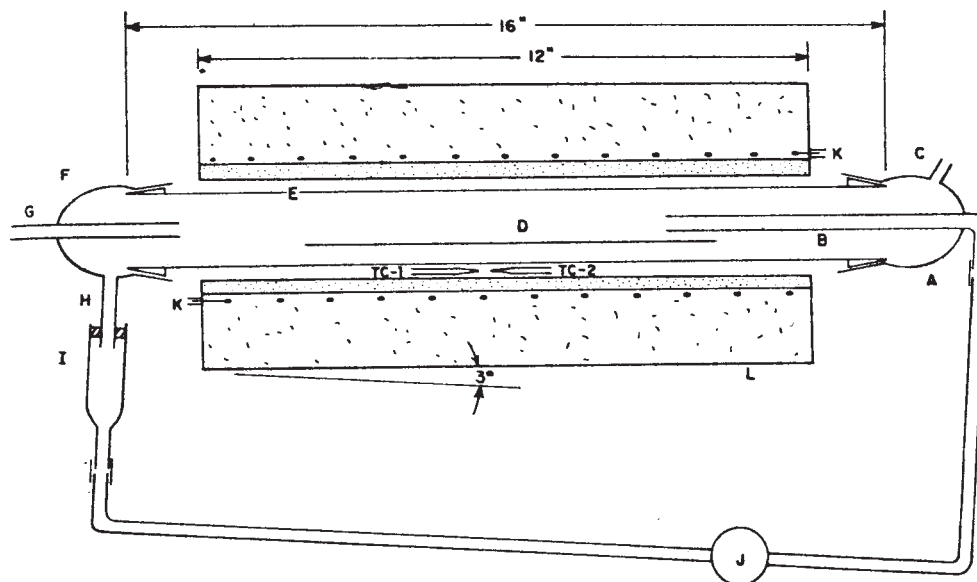


in.	mm
12	304.8
16	406.4

- A—Inlet end cap
- B—Sample delivery tube
- C—Gas atmosphere outlet
- D—Metal test piece for thin liquid films
- E—Furnace liner (with standard taper male end joints)
- F—Outlet end cap
- G—Gas atmosphere inlet
- H—Sample outlet tube
- I—Sample sump
- J—Peristaltic pump
- K—Insulated terminals of furnace heater element
- L—Tube furnace
- TC1—Control thermocouple for furnace controller
- TC2—Thermocouple for test temperature read out

FIG. 1 Tube Furnace

6.2 Furnace Liner (constant-temperature chamber)—See Fig. 2.

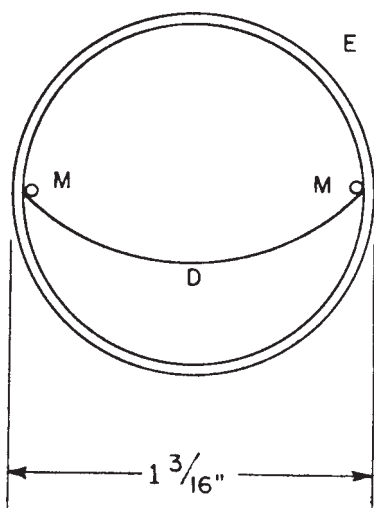

- 1 3/16 in. = 30.1 mm
- D—Metal test piece for thin liquid films
  - E—Furnace liner (with standard taper male end joints)
  - M—Longitudinal aligning rods

FIG. 2 Furnace Liner

6.3 Temperature Controller.<sup>9</sup>

6.4 Potentiometer, direct-temperature readout.<sup>10</sup>

6.5 Thermocouples, for temperature control and read-out in accordance with ANSI C96.1 (see Specification E 230).

6.6 Pump, peristaltic or kinetic clamp type capable of delivering  $50 \pm 5$  mL of sample per hour.<sup>11</sup>

6.7 Tubing<sup>12</sup> for use with pump.

6.8 Steel Test Specimens—See Fig. 3.

6.9 Analytical Balance capable of measuring mass of test specimen to the nearest 0.1 mg.

## 7. Reagents and Materials


7.1 Chloroform (**Warning**—Can be fatal if swallowed. Harmful if inhaled. May produce toxic vapors if burned. See A2.1.) technical grade.

<sup>9</sup> A Model 520 Solid State Controller manufactured by Barber Colman Co., Rockford, IL, has been found satisfactory.

<sup>10</sup> A Model 400A digital temperature indicator manufactured by Doric Scientific, San Diego, CA has been found satisfactory.

<sup>11</sup> Any peristaltic pump capable of delivering the sample at the prescribed rate is satisfactory. Any tubing compatible with the sample may be used. It is recognized that, due to viscosity and compatibility phenomena, no single pump and tubing combination will be acceptable for use with all samples.

<sup>12</sup> Kimwipes, Type 900M manufactured by Kimberly Clark Corp., Neenah, WI, have been found satisfactory.

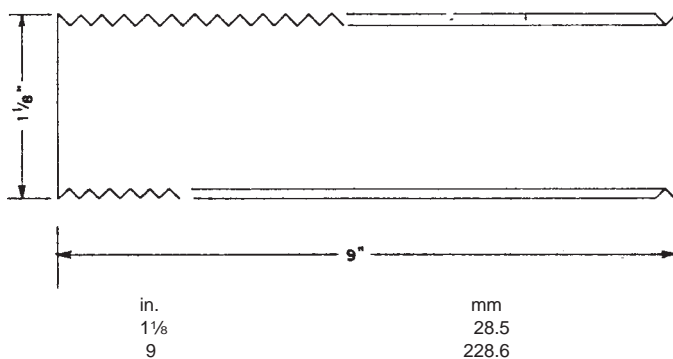

**FIG. 3 Metal Test Piece Thin Film Liquid Contact**

7.2 *Chromic Acid Cleaning Solution* (**Warning**—Causes severe burns. A recognized carcinogen. Strong oxidizer, contact with organic material can cause fire. Hygroscopic. See 2.2.)

7.3 *Mild Steel Shim Stock*, 0.051 mm (0.002 in.) thick.

7.4 *Pentane* (**Warning**—Extremely flammable. Harmful if inhaled. Vapors can cause flash fire. See A2.3.) commercial grade, conforming to the following requirements:

Distillation (Method D 216):	
Initial boiling point	306.5 K (92°F)
Dry point	313.8 K (105°F)
Olefins	none
Isopentane, max, %	20
<i>n</i> -Pentane, min, %	80
Reid vapor pressure (Test Method D 323), max	117 kPa (17 psi)

## 8. Sampling

8.1 The sample of test liquid shall be uncontaminated and representative of the bulk liquid as specified in Practice D 4057 or Test Method D 4177.

## 9. Test Specimens

9.1 One-hundred millilitres of a liquid test specimen are required for a single determination of the thin film deposit forming tendency.

## 10. Procedure

10.1 Prepare a test specimen in accordance with the following procedure:

10.1.1 Buff both sides of a piece of mild steel shim stock with jewelers rouge on a cloth wheel. The direction of polishing should be the same as that of the intended liquid flow.

10.1.2 Clean the shim stock thoroughly by washing with pentane and chloroform. Allow the specimen to dry at room temperature.

10.1.3 Cut a test specimen of the proper size from the polished stock (see Fig. 3).

10.1.4 Weigh the test specimen to the nearest 0.1 mg.

10.1.4.1 In order to clean the shim stock effectively it is necessary to wipe it vigorously with a paper tissue saturated with chloroform.

10.2 Clean the glass parts of the test apparatus by washing with hot chloroform. Tenacious deposits may be removed with chromic acid cleaning solution. Rinse thoroughly with water and dry the parts completely.

10.3 Insert the clean, dry test specimen in the furnace liner and place the liner in the furnace. Place the end caps on the liner. Install new tubing in the system. Fill the sump with 100 mL of the sample to be tested.

10.4 Before connecting the pump outlet tube to the input head of the furnace liner determine that the sample flow rate is  $50 \pm 5$  mL/h. If the flow rate is not within the stated limits adjust the rate accordingly until it is correct.

10.5 Turn on the furnace and allow it to reach temperature equilibrium at the desired test temperature. Start the sample pump at the same time.

10.5.1 A test temperature of 533 K has been found to be useful for the evaluation of the thin film deposit forming characteristics of automotive crankcase oils and similar materials of petroleum origin. Synthetic materials and highly refined petroleum fluids may be tested at higher temperatures if desired.

10.6 Allow the sample to circulate from the sump, over the test specimen and back to the sump for 5 h after the furnace has reached temperature equilibrium.

10.7 After 5 h turn off the pump and remove the test specimen from the furnace liner. Carefully rinse the test specimen with three successive rinses of pentane to remove adhering sample. Dry at room temperature and weigh to the nearest 0.1 mg. Then rinse the test specimen carefully with three successive rinses of chloroform. Dry at room temperature and weigh to the nearest 0.1 mg. Wipe the test specimen vigorously in the longitudinal direction with a piece of laboratory tissue to remove loose deposits. Weigh the test specimen to the nearest 0.1 mg.

10.7.1 Test periods longer or shorter than 5 h may be used provided that their use is noted in the report of test results.

10.7.2 Rinse the test specimen by immersion in the solvents. A spray of solvent from a wash bottle shall not be used, since it may cause the loss of loosely adhering deposits. Take care to avoid undue flexing of the exposed test specimen as this can also cause the loss of some of the deposit.

## 11. Calculations

11.1 Gross deposit, mg,

$$d_G = 1000 (M_G - M_O) \quad (1)$$

where:

$M_G$  = mass of liquid film test specimen plus deposit after rinse with pentane, g

$M_O$  = mass of liquid film test specimens before test after rinse with pentane and chloroform, g

$d_G$  = gross deposit from liquid film, mg

11.2 Chloroform-insoluble deposit, mg,

$$d_C = 1000 (M_C - M_O) \quad (2)$$

where:

$d_C$  = chloroform insoluble deposit from liquid film, mg

$M_C$  = mass of liquid film test specimens plus deposit after rinse with pentane and chloroform, g

11.3 Residual deposit, mg,

$$d_R = 1000 (M_R - M_O) \quad (3)$$

where:

- $d_R$  = residual deposit from liquid film, mg  
 $M_R$  = mass of liquid film test specimen plus deposit after rinse with pentane and chloroform and after abrasion with paper tissue to remove loose deposits, g

## 12. Report

12.1 Report the following information:

- 12.1.1 Temperature of test, K,  
 12.1.2 Test duration, h, if different from the specified time,  
 12.1.3 Composition of test panel, if different from the specified composition,

## 13. Precision and Bias

13.1 Because of the complex nature of this test method for deposition tendencies of liquids in thin films and vapors, there is not a sufficient number of volunteers to permit a cooperative laboratory program for determining the precision and bias. If the necessary volunteers can be obtained, a program will be undertaken at a later date.

## 14. Keywords

- 14.1 deposition tendency; deposits; thin films; vapors

# ANNEXES

## (Mandatory Information)

### A1. TEST METHOD FOR DETERMINATION OF VAPOR PHASE DEPOSITION TENDENCIES

A1.1 *Scope*—This annex covers the determination of the tendency of the vapors produced by the heating of lubricants, hydraulic fluids, heat-transfer fluids, and related materials to form deposits on metal surfaces. It is intended that the test shall measure the deposit formation tendencies of vapors on steel surfaces in air at 1 atm pressure. However, other surfaces and other atmospheric media may be substituted for steel and air at one atmosphere provided that the substitution is noted in the test report.

A1.2 *Summary of Test Method*—The sample is allowed to flow slowly in a thin film over a steel test specimen in a constant-temperature chamber. Circulation of the sample from the sump to the heated surface and back to the sump is accomplished by means of a peristaltic pump. A second test specimen is located in the vapor space over the thin liquid sample film. After the prescribed test period the test specimen in the vapor space is removed from the apparatus and evaluated. The mass of deposits remaining after washing with pentane, after washing with chloroform, and after wiping with a paper tissue are reported. The deposits formed by the liquid film may also be evaluated by the procedure described in 10.7.

#### A1.3 Symbols:

- $M'_O$  = mass of vapor space test specimen before test after rinse with pentane and chloroform, g.  
 $M'_F$  = mass of vapor space test specimen plus deposit after rinse with pentane, g.  
 $M'_C$  = mass of vapor space test specimen plus deposit after rinse with pentane and chloroform, g.  
 $M'_R$  = mass of vapor space test specimen plus deposit after rinse with pentane and chloroform and after abrasion with paper tissue to remove loose deposits, g.  
 $d'_G$  = gross deposit from vapor phase, mg.  
 $d'_C$  = chloroform insoluble deposit from vapor phase, mg.  
 $d'_R$  = residual deposit from vapor phase, mg.

A1.4 *Test Specimen*—One-hundred millilitres of a liquid

test specimen are required for a single determination of the vapor phase (and thin film) deposit forming tendency.


A1.5 *Apparatus*—The apparatus used for this test is the same as that described in Section 6 except that an additional vapor space test specimen (see Fig. A1.1 and Fig. A1.2) is used.

A1.6 *Materials*—The materials used for this test are the same as those described in Section 7.


#### A1.7 Procedure:

A1.7.1 Prepare the vapor space and liquid film test specimens in accordance with the procedures described in 8.1 and Fig. A1.2. Weigh the vapor space test specimen to the nearest 0.1 mg.

A1.7.1.1 If it is desired to determine the vapor phase and thin film deposition tendencies of the sample simultaneously, treat the liquid film test specimen in accordance with the procedures outlined in Sections 8 and 10.

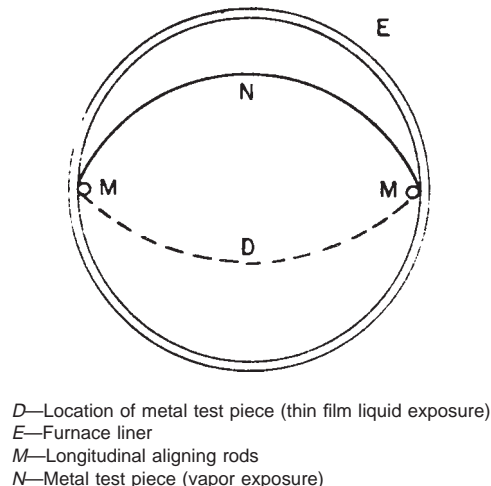

**FIG. A1.1 Vapor Phase**

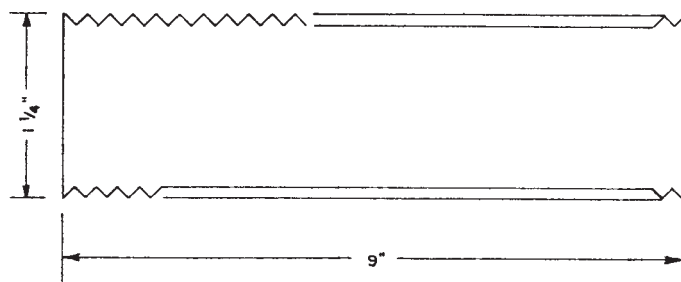

in.	mm
1/4	31.7
9	228.6

**FIG. A1.2 Metal Test Piece Vapor Contact**

A1.7.2 Clean the apparatus as described in 10.2 and insert the clean dry vapor phase and liquid film test specimen in the furnace liner. Assemble apparatus and adjust flow rates in accordance with 10.3 and 10.4.

A1.7.3 Turn on the furnace and allow it to reach temperature equilibrium at the desired test temperature. Start the sample pump at the same time.

A1.7.4 Circulate the sample from the sump over the liquid film test specimen and back to the sump for 5 h after the furnace has reached temperature equilibrium.

A1.7.5 After 5 h turn off the pump and remove the test specimen from the furnace liner. Measure the deposits on the vapor phase test specimen in accordance with 10.7.

## A2. PRECAUTIONARY STATEMENT

### A2.1 Chloroform:

**Warning**—Can be fatal if swallowed.

Harmful if inhaled. Can produce toxic vapors if burned.

Keep container closed.

Avoid prolonged breathing of vapor or spray mist.

Avoid contact with eyes and skin.

Do not take internally.

Use with adequate ventilation.

Can produce toxic vapors on contact with flames, hot glowing surfaces, or electric arcs.

### A2.2 Chromic Acid: (Cleaning Solution)

**Warning**—Causes severe burns. A recognized carcinogen.

Strong oxidizer; contact with organic material can cause fire.

Hygroscopic.

Do not get in eyes, on skin, on clothing.

Avoid breathing vapor or mist.

Keep container closed.

Use with adequate ventilation.

Do not take internally.

Wash thoroughly after handling.

Use protective clothing and goggles when handling.

### A2.3 Pentane:

**Warning**—Extremely flammable.

Harmful if inhaled. Vapors can cause flash fire.

Keep away from heat, sparks, and open flame.

Keep container closed.

Use with adequate ventilation.

Avoid buildup of vapors and eliminate all sources of ignition especially nonexplosion proof electrical apparatus and heaters.

Avoid prolonged breathing of vapor or spray mist.

Avoid prolonged or repeated skin contact.

*The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*