



Standard Test Method for Laboratory Evaluation of Wood and Other Cellulosic Materials for Resistance to Termites¹

This standard is issued under the fixed designation D 3345; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the laboratory evaluation of treated or untreated cellulosic material for its resistance to subterranean termites. This test should be considered as a screening test for treated material and further evaluation by field methods is required.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* For specific precautions, see 6.1.5.

2. Referenced Documents

2.1 ASTM Standards:

D 1413 Test Method for Wood Preservatives by Laboratory Soil-Block Cultures²

3. Apparatus

3.1 *Containers, Glass or Clean Plastic*, with loosely fitting tops with liners removed, 220 to 450 cm³ (8 to 16 oz).

3.1.1 If volatile chemicals are to be tested, a 4.8 mm (No. 12 or approx 3/16 in.) hole is drilled in the center of the top.

3.2 *Tray*, enamel, stainless steel, or plastic, 0.25 m by 0.51 m (10 by 20 in.) and bucket.

3.3 *Paper Towels*.

4. Reagents and Materials

4.1 *Benzalkonium Chloride Solution (1 + 750)*—Add 1 part benzalkonium chloride to 750 parts water. A comparable surface antiseptic is satisfactory.

4.2 *Distilled Water*.

4.3 *Sand*, brown or white, screened, washed, and heat-sterilized.

4.4 *Southern Yellow Pine (Pinus spp.)* measuring 25.4 mm (1.00 in.) square by 6.4 mm (0.25 in.) in the tangential

direction. Sapwood, no visible defects, smoothed surfaces equivalent to planed or sanded, 2 to 3 rings/cm (4 to 6 rings/in.). All test samples should come from same parent board.

4.4.1 Other wood species may be used, but in each separate test using other species as the major test wood, five southern yellow pine sapwood blocks should be used as additional controls to permit the correlation of test results among laboratories.

4.5 *Subterranean Termites*—Use a major common species of the region being studied.

4.5.1 Specific identification of any termites used shall be obtained and reported with the test data.

5. Determination of Sand Water-Holding Capacity

5.1 Determine the quantity of distilled water to be added to the sand during the test as follows:

5.1.1 Place 100 g of oven-dry sand in a beaker and determine the volume of water required to saturate the sand. The saturation point is defined as the point when the addition of more water will result in free water on the surface of the sand.

5.1.2 Calculate the percent saturation as follows:

$$\% \text{ Saturation} = (\text{weight of water/oven dry weight of sand}) \times 100 \quad (1)$$

5.1.3 Add water to the sand as follows:

$$\% \text{ water to add} = \text{saturation} - 7.0 \quad (2)$$

5.1.4 For example, the saturation point was reached at 20 mL of water:

$$\text{Saturation} = (20/100) \times 100 = 20.0 \% \quad (3)$$

$$\% \text{ Water to add} = 20.0 - 7.0 = 13.0 \%$$

6. Collection of Termites

6.1 *Subterranean Termites*, for example, (*Reticulitermes*, *Coptotermes*, spp.)—Collect from a large colony (over 50 000) in a natural forest situation, for example, from fallen logs, stumps, etc, or from strong laboratory cultures.

¹ This test method is under the jurisdiction of ASTM Committee D-7 on Wood and is the direct responsibility of Subcommittee D07.06 on Treatments for Wood Products.

Current edition approved Aug. 30, 1974. Published October 1974.

² *Annual Book of ASTM Standards*, Vol 04.10.

6.1.1 Remove short log sections to the laboratory and split them. Shake the insects out onto a tray or trays. After distributing the debris and insects evenly on the tray(s), lay damp paper towels, sheets of kraft paper, etc, over the debris. The termites will cling to the damp paper after a few minutes.

6.1.2 Prepare a 8 to 11-L (2 to 3-gal) pail by placing about ten unfolded slightly crumpled, damp paper towels in the bottom of the pail. Rinse these towels in distilled water and squeeze damp a number of times. Cover these towels with about ten unfolded, dry paper towels.

6.1.3 Shake the damp towels covering the tray debris into the above described pail. After 2 to 4 h, remove the dry towels and any insects and debris on them from the pail and discard. Use insects clinging to the lower, damp towels in the test.

6.1.4 Do not hold termites in the pail longer than 24 h before using.

6.1.5 **Caution:** Exercise reasonable care to ensure that any termites discarded (for example, 6.1.3) are dead. Ovendrying debris and towels used at 100°C for 6 h is sufficient. When a test is finished, reasonable care should also be exercised that living insects are not discarded.

7. Weathering of Test Blocks

7.1 If the test material is weathered prior to exposure to the insects, report the complete details on the weathering.

7.2 The ASTM weathering procedure for the soil-block test is recommended (see Method D 1413).

8. Conditioning of the Test Blocks

8.1 Condition all test blocks, following weathering if used, to a constant weight within the equilibrium moisture content range from 6 to 14 % moisture content to ensure that all solvent is removed prior to exposure to insects.

8.2 The ASTM soil-block conditioning procedure is recommended (see Method D 1413).

9. Block Quantity and Identifications

9.1 Prepare five replicate blocks for each variable under test, for example, for each retention of each preservative or chemical to be tested.

9.2 Use five untreated blocks as described in 9.1 as controls for each separate study.

9.3 If a southern yellow pine (SYP) is not used as the species in 9.1 and 9.2, then add five blocks of untreated SYP to each study to permit a comparison to studies using SYP as the major species.

9.4 Identify all blocks with a number in a suitable manner.

10. Assembling Containers

10.1 Prior to using, wash all containers rinsed in the surface antiseptic solution, and dry.

10.2 Place the test block in the bottom of the container with one edge of the block up against the side of the container.

10.3 Add 200 g of sand to each container.

10.4 Use suitable numbers on each container.

10.5 Add sufficient distilled water to each container as determined in Section 5. After addition of the water, allow the containers to stand overnight.

10.6 Assemble five containers with sand, water, and termites but without test blocks.

11. Adding Termites

11.1 Weigh out 1 ± 0.05 g of subterranean termites (Section 6) and add to each of the previously prepared containers. Select the termites so that about 90 % are workers.

11.2 Replace the container tops loosely.

12. Container Storage and Inspections

12.1 Select five test containers randomly and weigh individually. Maintain all containers at 25.5 to 27.7°C (78 to 82°F) for 4 weeks.

12.2 At the end of the first and fourth weeks, examine the containers and record the presence of tunneling, termite mortality, and position of the termites in the container as follows:

12.2.1 After 1 week, containers assembled in accordance with 10.6 should show virtually complete survival, thereby indicating that test procedures have been followed and vigorous termites used.

12.2.2 *Tunneling Present, yes, no.* (Tunneling indicates vigor of insects.)

12.2.3 *Majority Termite Position*—(On or beneath surface. Position on surface suggests response of termites to an antagonizing effect such as repellency of preservative.)

12.2.4 *Approximate Termite Mortality*—Slight (0 % to 33 %), moderate (34 % to 66 %), heavy (67 % to 99 %), complete (100 %).

12.2.5 Weekly reweigh the five selected containers (12.1) and add distilled water to all containers if the moisture content of the sand drops below two percentage points of the original moisture content (see Section 5).

13. Container Disassembly

13.1 After 4 weeks disassemble the containers and remove and clean the blocks. Prior to and during the disassembly, note the items in 12.2. Discard the used sand and termites (see 6.1.5) and do not reuse for subsequent tests.

14. Block Evaluation

14.1 Examine and visually rate each block using the following rating system:

10	Sound, surface nibbles permitted
9	Light attack
7	Moderate attack, penetration
4	Heavy
0	Failure

14.2 Blocks representative of these levels of attack are shown in Fig. 1.

15. References

15.1 In general, details of the Method D 1413 or AWP Standard M 10 (they are identical) should be used for treating procedure and any other items in question not specifically mentioned in the above detailed termite test method.

16. Keywords

16.1 cellulosic materials; termites; wood

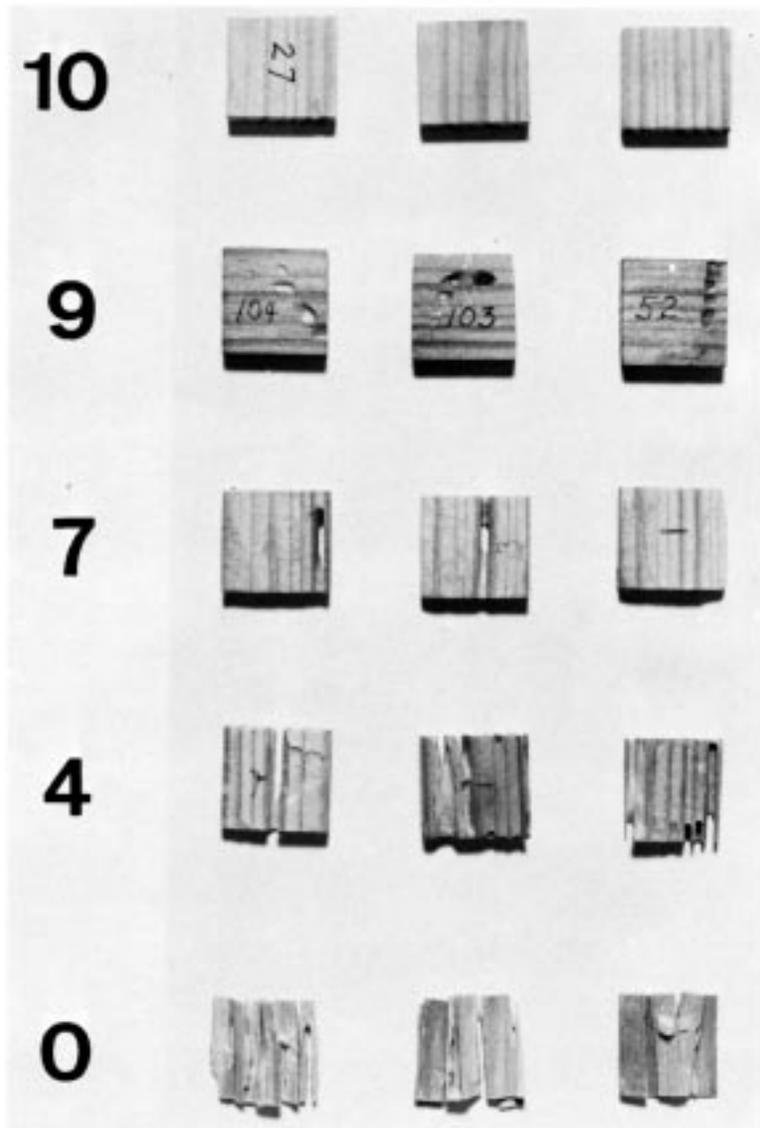


FIG. 1 Typical Ratings of Termite Attack on Test Blocks

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).