



Standard Test Method for Spiral Flow of Low-Pressure Thermosetting Molding Compounds¹

This standard is issued under the fixed designation D 3123; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

^{e1} NOTE—Editorially replaced reference to Practice D 1898 with Practice E 105 in April 2000.

1. Scope

1.1 This test method covers a procedure for measuring the spiral flow of thermosetting molding compounds (soft or very soft) designed for molding pressures under 6.9 MPa (1000 psi). It is especially suited for those compounds that may be used for encapsulation or other low pressure molding techniques. Textile-reinforced compounds should not be tested using this test method. It involves the use of a standard spiral flow mold in a transfer molding press under specified conditions of applied temperature and pressure with a controlled charge mass.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

NOTE 1—There is no equivalent ISO standard.

2. Referenced Documents

2.1 ASTM Standards:

D 883 Terminology Relating to Plastics²

D 958 Practice for Determining Temperatures of Standard ASTM Molds for Test Specimens of Plastics²

E 105 Practice for Probability Sampling of Materials³

3. Terminology

3.1 *Definitions*—Definitions in this test method are consistent with Terminology D 883.

¹ This test method is under the jurisdiction of ASTM Committee D-20 on Plastics and is the direct responsibility of Subcommittees D20.30 on Thermal Properties (Section D20.30.08).

Current edition approved March 10, 1998. Published January 1999. Originally published as D 3123 – 72. Last previous edition D 3123 – 94.

² *Annual Book of ASTM Standards*, Vol 08.01.

³ *Annual Book of ASTM Standards*, Vol 14.02.

4. Significance and Use

4.1 The spiral flow of a thermosetting molding compound is a measure of the combined characteristics of fusion under pressure, melt viscosity, and gelation rate under specific conditions.

4.2 This test method is useful as a quality control test and as an acceptance criterion.

4.3 This test method, by itself, is not a valid means for comparing the moldability of similar or different molding compounds because it cannot duplicate actual conditions prevalent in different types of production molds.

4.4 This test method is presently intended for use at a transfer pressure of 6.9 MPa (1000 psi) and a mold temperature of 423 ± 3 K ($(150 \pm 3^\circ\text{C})$ ($302 \pm 5^\circ\text{F}$)).

5. Apparatus

5.1 *Transfer Molding Press* with a minimum 150 by 150-mm (6 by 6-in.) platen area, transfer piston pressure potentially greater than 6.9 MPa (1000 psi), sufficient clamp pressure to prevent flashing, and a minimum plunger speed of 25.4 mm (1 in.)/s without load. The plunger should be equipped with at least one peripheral sealing groove. It is recommended that a pot diameter between 31.75 and 44.45 mm (1.25 and 1.75 in.) be used whenever a choice is possible.

NOTE 2—Preliminary evidence indicates that, in many cases, reasonable correlations may be achieved between laboratories using presses with different pot diameters. Typical examples are presses with pot diameters of 31.750, 38.100, and 44.450 mm (1.250, 1.500, and 1.750 in.). However, a few well-documented cases are recorded where differences in pot diameters, even within this listed range, have caused large differences in flow-length readings. Therefore, for best interlaboratory correlation it is recommended that identical pot diameters be used.

5.2 *Standard Spiral-Flow Mold* shown in Fig. 1 shall be utilized.

6. Materials

6.1 *Molding Compound:*

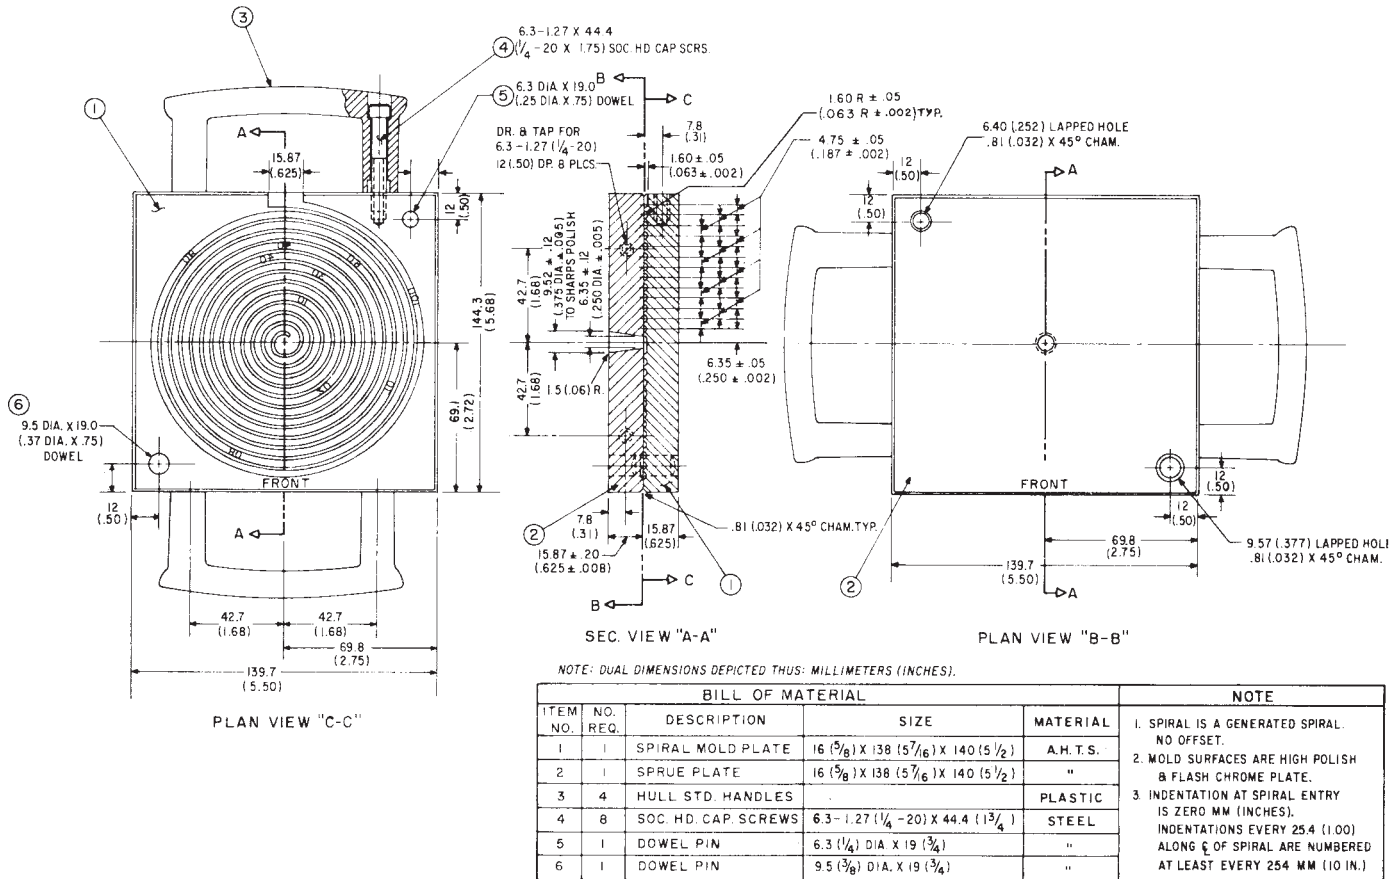


FIG. 1 Standard Spiral-Flow Mold

6.1.1 Any thermosetting molding compound with a spiral flow between 762 and 1270 mm (30 and 50 in.) as determined at the standard temperature and pressure of this test can be evaluated.

NOTE 3—Since the only commercially available molds are calibrated in inches, spiral-flow length will be reported in these units. Conversion to SI units can readily be made by multiplying the flow length, in inches, by the appropriate conversion factor, 25.4 mm/in.

NOTE 4—There is considerable evidence that the test is usable over a wider range of flow lengths, but this has not yet been confirmed by interlaboratory testing.

6.1.2 Form—The form of the molding compound shall be loose powder or granules at 296 ± 2 K ($(23 \pm 2^\circ\text{C})$ ($73.4 \pm 3.6^\circ\text{F}$)).

NOTE 5—Preforms or pellets may be used if found necessary; however, flow length may be affected by their use.

7. Sampling

7.1 Unless otherwise agreed upon between the seller and purchaser, sampling shall be in accordance with Practice E 105. Sampling, based on engineering principles, prior to packaging shall be considered an acceptable alternative.

8. Conditioning

8.1 Conditioning—All molding compounds shall be tested in “as-received” condition. For referee testing, all material shall be shipped and stored in moisture-barrier containers.

They shall be stored for a minimum of 24 h at the standard laboratory temperature, before breaking the seal on the container. Care should be taken to preserve the “as-received” moisture content and tests shall be made as soon as possible once the container has been opened. Alternative methods of conditioning samples may be used, provided they are mutually agreed between manufacturer and purchaser.

9. Test Conditions

9.1 Spiral-Flow Mold—The mold shall be clean and free from any mold-release agents or lubricants. Several preliminary moldings shall be made with the material to be tested to purge the helical runner before beginning the test. This procedure is essential when changing from one compound to another and is recommended as a routine practice.

9.2 Molding Conditions:

9.2.1 Temperature—A temperature of 423 ± 3 K ($(150 \pm 3^\circ\text{C})$ ($302 \pm 5^\circ\text{F}$)) shall be maintained on the mold and transfer plunger. The temperature may be measured in accordance with the procedures described in Practice D 958 or by thermocouples attached to the mold and plunger. The temperature should be allowed to reach equilibrium by waiting at least 3 min between moldings.

9.2.2 Transfer Pressure—The actual pressure applied to the compound at the base of the pot shall be 6.90 ± 0.17 MPa (1000 ± 25 psi). In most presses the gage pressure is not

sufficiently accurate for determining transfer pressure. Therefore, the force exerted by the plunger shall be measured by some means such as an accurately calibrated direct-reading force gage or proving ring. The actual transfer pressure is then calculated as pascals (or pounds per square inch) by dividing the force in newtons (or pounds-force) by the plunger area in square metres (or square inches).

9.2.3 *Charge Mass*—The mass of the compound shall be determined empirically so that the thickness of the molded cull (cured compound on top of the sprue plate of the mold), after test, is between 3 and 3.5 mm (0.12 and 0.14 in.). The relationship between the amount of compound and the dimensions of the transfer pot is critical in obtaining meaningful, reproducible spiral-flow values. The use of excessive amounts of compound will result in shorter, inconsistent spiral flows. For transfer pots 31.75 to 44.45 mm (1.25 to 1.75 in.) in diameter, 20 g of compound is suggested as the starting charge mass.

9.2.4 *Transfer Plunger Speed*—The transfer plunger speed without load (as described in 5.1) shall be controlled between 25 and 100 mm/s (1 and 4 in./s). The elapsed time between insertion of the charge into the pot and the development of pressure on the charge by the plunger shall be no more than 5 s. Too long a dwell time before transferring will cause erratic results.

9.2.5 *Press Cure Time*—Sufficient cure time shall be used to facilitate easy removal of the spiral from the mold. This time will vary with the compound under test. Manufacturer's recommendations for cure should be followed.

9.2.6 *Transfer Plunger Grooves*—If the transfer plunger is equipped with grooves, they must be cleaned before each new molding.

9.3 *Flow Length*—Flow length shall be the farthest point at which the material completely fills the cross section of the helix runner.

10. Procedure

10.1 Heat the mold and transfer the plunger to 423 ± 3 K ($(150 \pm 3^\circ\text{C})$ ($302 \pm 5^\circ\text{F}$)).

10.2 The plunger preferably is equipped with sealing grooves. These must be cleaned free of compound before checking pressure and before each molding.

10.3 Using a force gage or proving ring, adjust the transfer pressure to 6.90 ± 0.17 MPa (1000 ± 25 psi).

10.4 Weigh out the compound to the nearest 0.1 g as previously determined to yield a 3 to 3.5-mm (0.12 to 0.14-in.) molded cull.

10.5 Place the compound in the transfer pot and activate the transfer cycle immediately. Cure the compound as recommended for easy removal.

10.6 Open mold and remove the cured material. Read the spiral flow length directly from the molded specimen at the point of farthest continuous flow to the nearest 0.25 in. (Note 3).

10.7 Repeat 10.4 to 10.6 until three consecutive flow readings agree to within $\pm 5\%$ of their average.

11. Report

11.1 Report the following information:

11.1.1 The accurate identity of the sample tested,

11.1.2 Average spiral-flow length reported to the nearest 6.35 mm (0.25 in.),

11.1.3 The temperature and pressure used for the test,

11.1.4 The form of the material (granulated, preformed, etc.),

11.1.5 The average cull thickness and charge mass used, and

11.1.6 The ram diameter and speed.

12. Precision and Bias

12.1 Statistical analysis of round-robin data⁴ indicates that within a given laboratory the averages of three flow length determinations on a typical material will not differ from each other by more than 1.29 in. at a 95 % confidence level. An accurate estimate of the reproducibility between laboratories is currently unavailable.

13. Keywords

13.1 spiral flow; thermosets

⁴ Round-robin data for this test method are available from ASTM Headquarters. Request RR: D20-1028.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).